



## **1 Introduction**

STMicroelectronics supports various lead-free package types to adapt MCUs to customer requirements.

Beside the available mounting technology (SMD or Through Hole), the choice is often driven by technical and economical concerns. This application note describes the various package types used for MCUs, introduces the various mounting technologies and gives soldering recommendations.

---

## Contents

<b>1</b>	<b>Introduction</b> .....	<b>1</b>
<b>2</b>	<b>Lead-free packages at STMicroelectronics</b> .....	<b>3</b>
<b>3</b>	<b>Microcontroller packages</b> .....	<b>4</b>
<b>4</b>	<b>SMD presentation</b> .....	<b>5</b>
	4.1 Handling SMDs .....	5
<b>5</b>	<b>Soldering</b> .....	<b>6</b>
	5.1 Soldering methods .....	6
	5.2 Soldering recommendations .....	7
	5.3 Compatibility with leaded soldering process .....	7
	5.4 Reflow soldering conditions .....	8
<b>6</b>	<b>SMD gluability</b> .....	<b>10</b>
<b>7</b>	<b>Dry packing</b> .....	<b>11</b>
<b>8</b>	<b>Revision history</b> .....	<b>14</b>

## 2 Lead-free packages at STMicroelectronics

STMicroelectronics is fully committed to environment protection and sustainable development and started in 1997 a voluntary program for removing polluting and hazardous substances from all devices. In 2000, a strategic program, named ECOPACK™ has been officially launched to develop and implement solutions leading to environment friendly packaging and ban progressively Pb and other heavy metals from our manufacturing lines. Ecopack is a registered trade-mark of STMicroelectronics.

STMicroelectronics ECOPACK products are RoHS Compliant according to EU 2002/95/EC directive (1).

For more detailed information please connect to <http://www.st.com>

*Note: (1) RoHS = Restriction of the use of certain Hazardous Substances*

*The directive 2002/95/EC of the European Parliament and of the Council of 27th January 2003 on the RoHS in electrical and electronic equipments entered into force on 13th of February 2003. The aim of this directive is to ban heavy metals (Lead, Mercury, Cadmium, Hexavalent Chromium, Ö) and two brominated compounds (PBB and PBDE). The directive will be applicable throughout EU by 1st July 2006.*

### 3 Microcontroller packages

The different packages generally available at STMicroelectronics (for microcontrollers) are detailed in the following table (2):

**Table 1. Microcontroller package types <sup>(1)</sup>**

Surface mount technology		Throug Hole Technology	
Package	Pin Count	Package	Pin Count
SON	8,16	PDIP .3	8, 16, 20
SOW	16, 20, 24, 28, 34 Shrink	PDIP .4	32S
PLCC	44, 520	PDIP .6	28, 42S, 56S
PQFP	44, 52, 80, 100, 144, 208		
LQFP	32, 44, 48, 52, 64, 80, 100, 128		
LFBGA,TFBGA	Up to 144		
PBGA	Up to 480		
VFQFPN	8, 20, 24, 40, 48		

1. Larger package portofolio can be proposed upon request.

**Through Hole Technology (THT)** and **Surface Mount Technology (SMT)** imply different soldering technologies leading to different constraints.

In THT, the package body is exposed to relatively low temperatures (< 150 °C) because the lead extremities are only dipped in the soldering alloy whereas in SMT, the whole package body is exposed to a very high temperature (> 240 °C) during reflow soldering process.

Furthermore, molding compounds used for integrated circuit encapsulation absorb moisture from the ambient medium. During rapid heating in solder reflow process (see further for more details), this absorbed moisture can vaporize, generating pressure at lead frame pad / silicon to plastic interfaces in the package, with a risk of package cracking and potential degradation of device reliability.

## 4 SMD presentation

Unlike throughhole technology that inserts leads into the printed circuit board, SMD package is attached directly onto mounting pads of the substrate. Surface Mount Technology is extensively used in electronic applications because it has the following advantages:

- Packages are smaller and support higher pin counts
- Packages are light and compact, thus reducing system sizes
- Mounting can be done on either side of the PCB
- No cost for drilling holes into the PCB

Surface mount technology also comes along with a few disadvantages:

- Increased sensitivity to soldering heat because of their thinner dimension
- Soldering conditions harder to determine (use of finer structures and higher pin count)

### 4.1 Handling SMDs

Though the intrinsic reliability of SMD packages is now excellent, the use of inappropriate techniques or unsuitable tools during mechanical handling can affect the long term reliability of the device, or even destroy it.

When handling a SMD package, it is strongly recommended to use adapted tools such as vacuum pipes to avoid touching the pins as much as possible. Manual handling could affect lead coplanarity and cause lead contamination or scratches that could generate solderability problems. It is also not allowed to widen the interval between two consecutive pins.


# 5 Soldering

## 5.1 Soldering methods

There are 3 main soldering methods (which are detailed on the following graph):

1. Single sided reflow soldering
2. Double sided reflow soldering
3. Wave soldering (for THT devices)

Figure 1. Soldering method descriptions

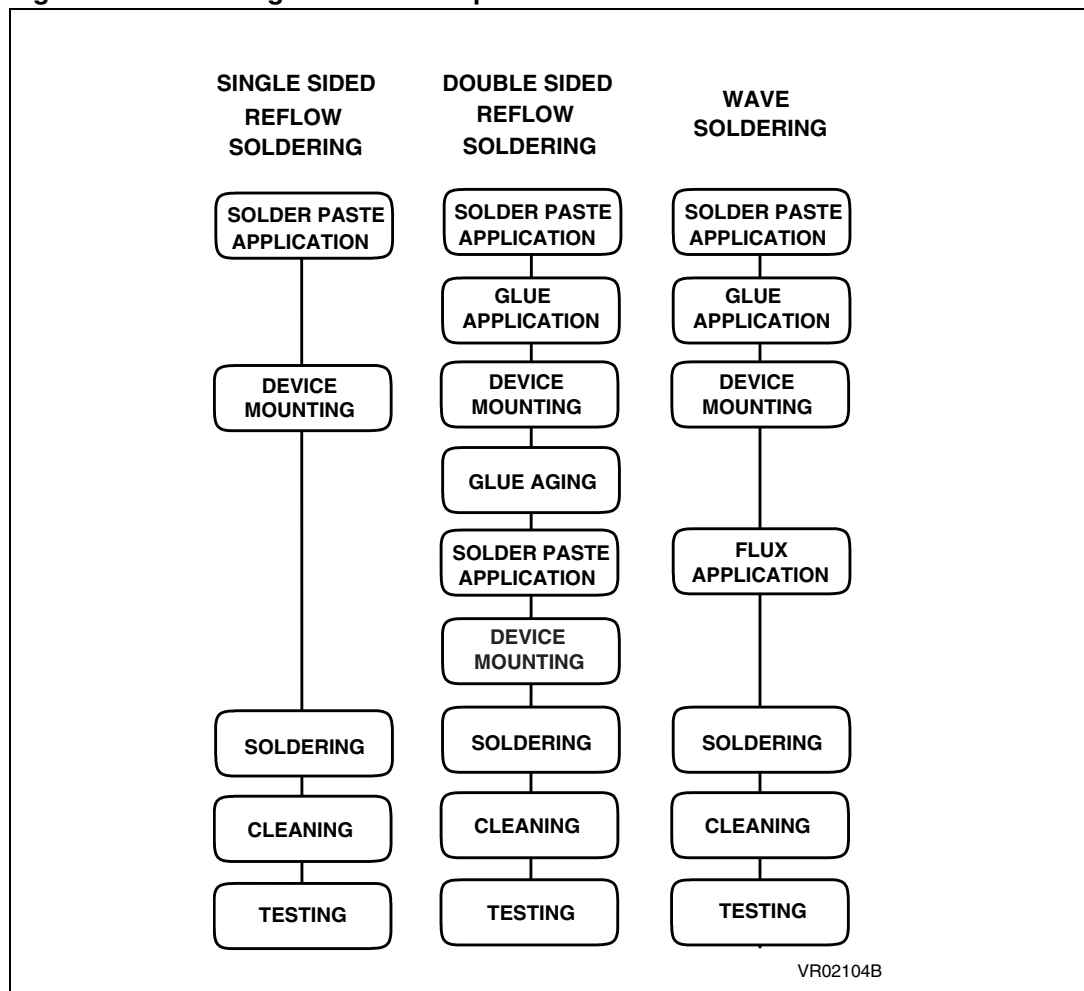

## Bending leads

In all processes it is important to avoid straining the package and particularly the area where the leads enter the encapsulating resin. If the package / lead interface is strained the resistance to humidity and thermal stress will be compromised, affecting device reliability.

## Insertion

When mounting devices on a printed circuit board the golden rule is, again, to avoid stress. In particular, adhere to the specified pin spacing of the device: do not try to bend the leads to fit non-standard hole spacing.

## 5.2 Soldering recommendations

The following recommendations must be followed for soldering each package type:

**Table 2. Package/soldering process compatibility**

Package	Reflow processing process		Wave soldering process	
	Process	Reliability	Process	Reliability
PLCC	OK	OK	impossible	N/A
SOP	OK	OK	feasible	see note <sup>(1)</sup>
QFP	OK	OK	critical , see note <sup>(2)</sup>	see note <sup>(1)</sup>
BGA	OK	OK	impossible	N/A
VFQFPN	OK	OK	impossible	N/A

1. Wave soldering with SMT packages is not recommended because the thermal shock associated with package body solder dipping may induced internal structural damage to the package (interface delamination) that may affect long term reliability.

SMT Package characterizations performed as a standard by STMicroelectronics only include Solder Reflow Resistance assessment.

JEDEC JESD22A111 recommends that wave soldering of SMT packages should be evaluated by the USER, because the stress induced inside the package is very dependant of solder process parameters.

2. Wave soldering with PQFP is not recommended because it is difficult to avoid solder bridges when leads pass through the double wave.

*Note: Reflow soldering with DIP and wave soldering with PLCC, BGA and VFQFPN are strictly impossible due to the lead/ball configuration.*

## 5.3 Compatibility with leaded soldering process

Lead-free packages can be assembled using leaded soldering process. For more details about soldering process compatibilities and conditions, please refer to Application note AN2034.

## 5.4 Reflow soldering conditions

The greater danger during reflow soldering is overheating. If an integrated circuit is exposed to high temperature for an excessive period it may be damaged and its reliability reduced.

It is also important to use suitable fluxes for the soldering baths to avoid deterioration of the leads or package resin. Residual flux between the leads or in contact with the resin must be removed to guarantee long term reliability. The solvent used to remove excess flux should be chosen with care. In particular, trichloroethylene (CHCl: CCl<sub>2</sub>) - base solvents should be avoided because the residue could corrode the encapsulating resin.

High quality, low defect soldering requires identifying the optimum temperature profile for reflowing the solder paste, therefore optimizing the process. The heating and cooling rise rates must be compatible with the solder paste and components.


A typical profile consists of a preheat, dryout and reflow sections.

The most critical parameter in the preheat section is to minimize the rate of temperature rise to less than 2°C / second, in order to minimize thermal shock on the semiconductor components.

Dryout section is used primarily to ensure that the solder paste is fully dried before hitting reflow temperatures.

Solder reflow is accomplished in the reflow zone, where the solder paste is elevated to a temperature greater than the melting point of the solder. Melting temperature must be exceeded by approximately 20° C to ensure quality reflow.

**Figure 2. Typical reflow soldering profile**

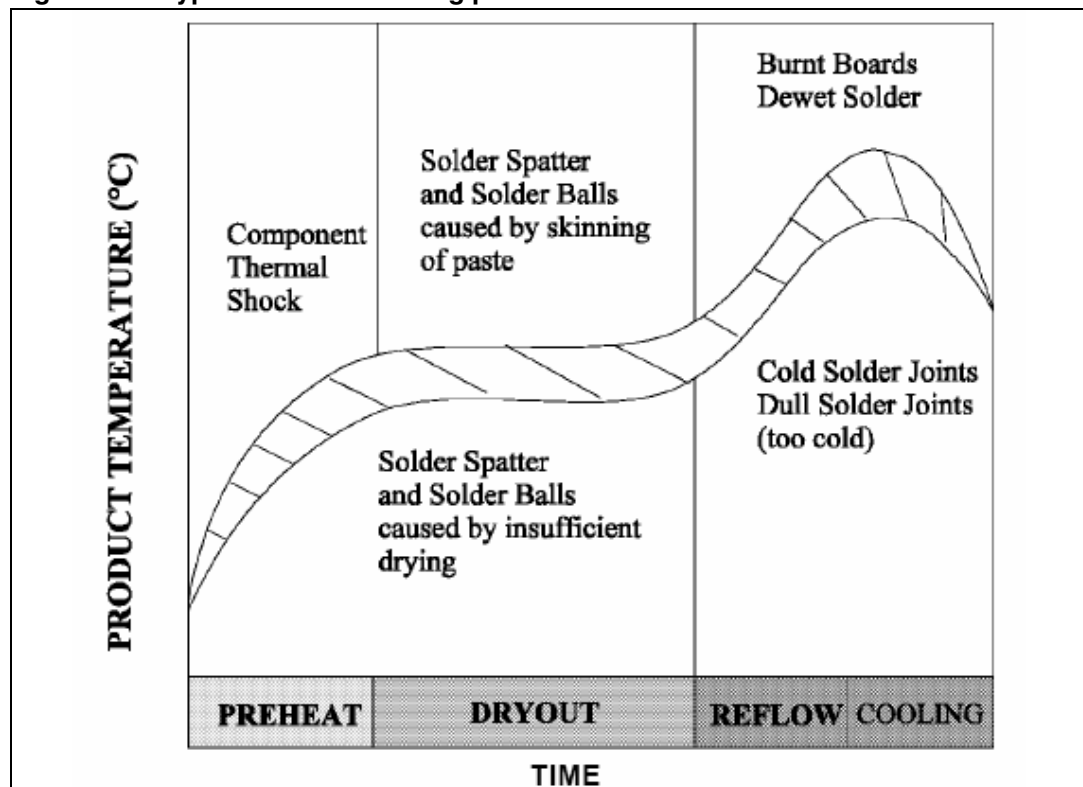




Here are the recommended profiles for reflow soldering.

STMicroelectronics lead-free packages are warranted for such reflow profile conditions.

**Figure 3. Recommended reflow soldering profile**

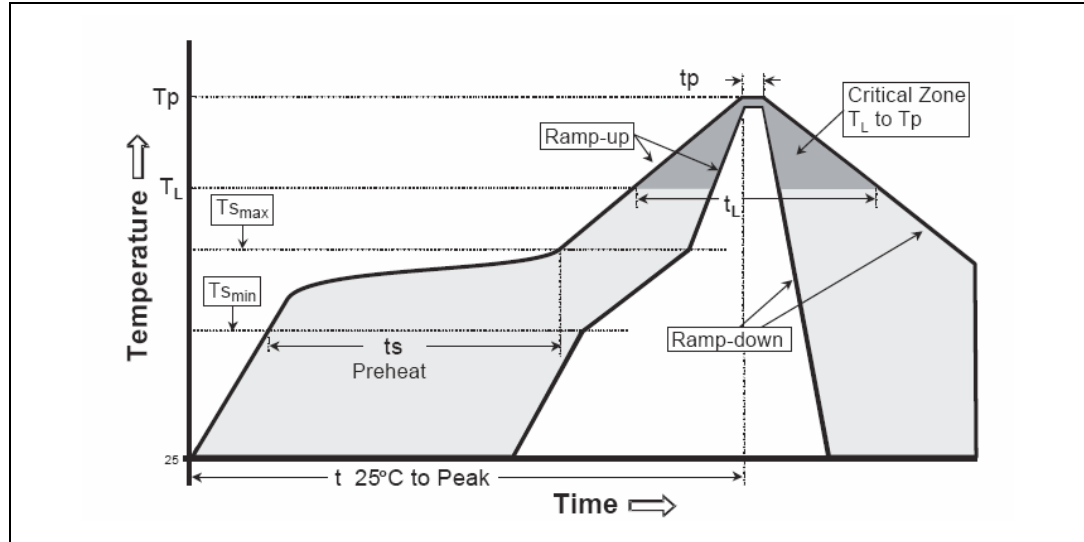

**Table 3. Jedec standard lead-free reflow profile (according to J-STD-020C) <sup>(1)</sup>**


Profile feature	Pb-Free Assembly
Average Ramp-Up Rate (Tsmmax to Tp)	3°C/second max.
Preheat -Temperature Min (Tsmmin) -Temperature Max (Tsmmax) -Time (tL)	150°C 200°C 60-180 seconds
Time maintained above: -Temperature (TL) -Time (tL)	217°C 60-150 seconds
Peak/Classification Temperature (Tp)	Package dependant, see temperature indicated on box label.
Time within 5°C of actual Peak Temperature (Tp)	20-40 seconds
Ramp-Down Rate	6°C/second max.
Time 25°C to Peak Temperature	8 minutes max.

1. All temperatures refer to topside of the package, measured on the body surface


## 6 SMD gluability

We strongly recommend our customers to follow glue application specifications from their glue supplier. We also recommend 100% glue polymerization for optimal glue efficiency.

**Figure 4. Recommended profiles for glue polymerization using regular oven and linear flow oven**

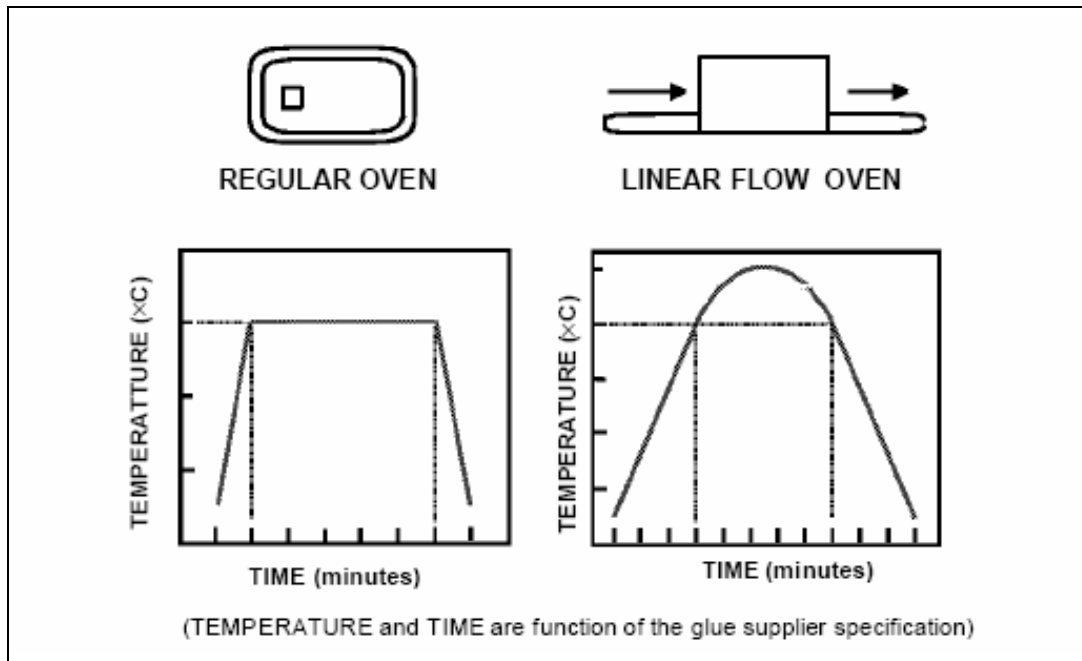

**Figure 5. Gluability evaluation with a shear test**

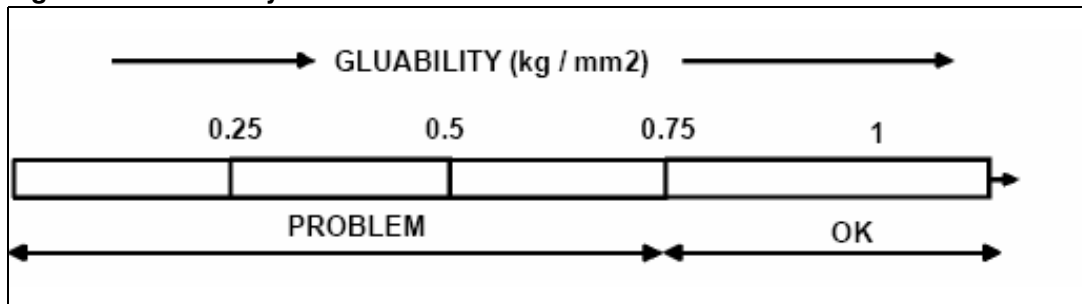

Various tests have shown that glue shear test specification limit conforms to the IPC SM817 standard (0.75 kg / mm<sup>2</sup> minimum). Customer complaints usually happen when values are below 0.5 kg / mm<sup>2</sup>. It has been verified that below 0.25 kg / mm<sup>2</sup> components fall from PCB during handling. General capability in plastic SMD is greater than 1 kg / mm<sup>2</sup>.

## 7 Dry packing


Quality and reliability of SMDs after soldering depends heavily on moisture absorption during storage. A specific packing, called Dry-Pack, was implemented for defined conditions at the delivery. Time and environment will modify the amount of absorbed humidity. Moisture sensitive Surface Mount Devices (SOP, PLCC, PQFP, BGA, VFQFPN) are dry packed to protect them from moisture absorption during shipment / storage and then to reduce failure risks mainly due to popcorn effect.

Pop-corn effect. Pop-corn effect is the cracking of the package during the soldering cycle. It has got a growing importance due to the trends towards larger die size in integrated circuits. This phenomenon is mainly caused by the moisture absorbed by the epoxy molding. When the package is exposed to high temperatures, as in most SMT soldering processes, the water at the interface between plastic and die pad vaporizes suddenly, generating high internal pressure. Cracks may occur in the molding compound depending on the absorbed moisture level, soldering temperature and time, die size, package structure and molding compound characteristics.

SMD products are contained in tubes, on trays or on tape, and are then vacuum sealed in an hermetic bag.

Opening the package will stop the ideal conditions and start the influence of the normal environment. The following diagram shows the recommended handling flow.

Figure 6. Recommended flow to control package moisture absorption

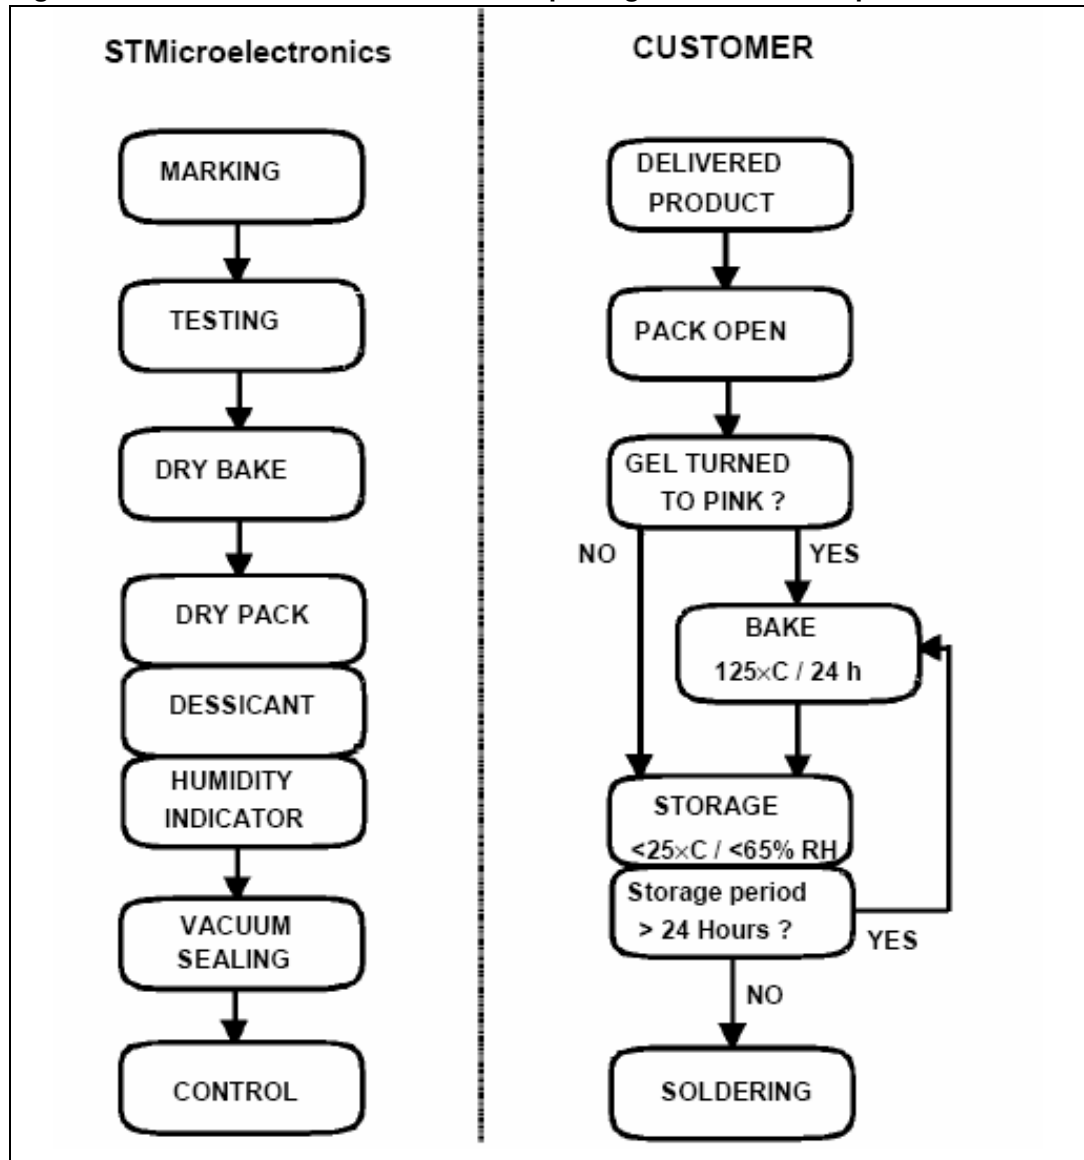

Parts with Dry Pack are recommended to be stored in Dry Boxes (i.e. cabinets under nitrogen atmosphere). When no dry boxes are available, the following environmental conditions are recommended for storage:

Table 4. Environmental conditions


Temperature	5 -> 30°C
Humidity	60°C max

Dust should also be minimized. There should be no vibration or shock which could distort the packing container. To avoid excess weight packing, containers should not be stacked on top of each other.

**Dry Pack Opening.** After opening a dry pack, soldering should be done within a 24 hours period. SMD products stored over the specified storage period need to be

baked at 125°C for 24 hours (under nitrogen atmosphere). Devices packed in tubes or in tapes must be transferred to metal tubes before baking whereas trays are bake able.

**Figure 7. Moisture absorption / drying curve.**

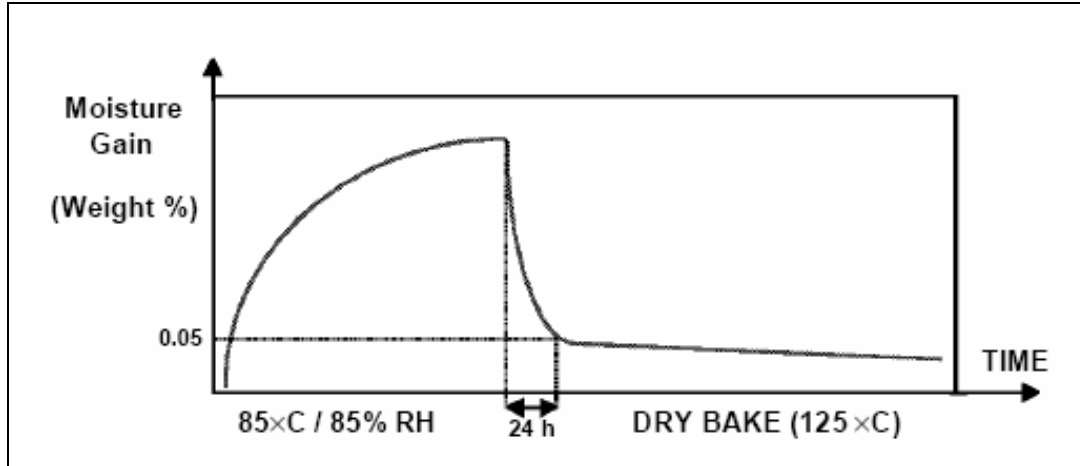

## 8 Revision history

**Table 5. Document revision history**

Date	Revision	Changes
16-Oct-2007	1	Initial release

**Please Read Carefully:**

Information in this document is provided solely in connection with ST products. STMicroelectronics NV and its subsidiaries ("ST") reserve the right to make changes, corrections, modifications or improvements, to this document, and the products and services described herein at any time, without notice.

All ST products are sold pursuant to ST's terms and conditions of sale.

Purchasers are solely responsible for the choice, selection and use of the ST products and services described herein, and ST assumes no liability whatsoever relating to the choice, selection or use of the ST products and services described herein.

No license, express or implied, by estoppel or otherwise, to any intellectual property rights is granted under this document. If any part of this document refers to any third party products or services it shall not be deemed a license grant by ST for the use of such third party products or services, or any intellectual property contained therein or considered as a warranty covering the use in any manner whatsoever of such third party products or services or any intellectual property contained therein.

**UNLESS OTHERWISE SET FORTH IN ST'S TERMS AND CONDITIONS OF SALE ST DISCLAIMS ANY EXPRESS OR IMPLIED WARRANTY WITH RESPECT TO THE USE AND/OR SALE OF ST PRODUCTS INCLUDING WITHOUT LIMITATION IMPLIED WARRANTIES OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE (AND THEIR EQUIVALENTS UNDER THE LAWS OF ANY JURISDICTION), OR INFRINGEMENT OF ANY PATENT, COPYRIGHT OR OTHER INTELLECTUAL PROPERTY RIGHT.**

**UNLESS EXPRESSLY APPROVED IN WRITING BY AN AUTHORIZED REPRESENTATIVE OF ST, ST PRODUCTS ARE NOT DESIGNED, AUTHORIZED OR WARRANTED FOR USE IN MILITARY, AIR CRAFT, SPACE, LIFE SAVING, OR LIFE SUSTAINING APPLICATIONS, NOR IN PRODUCTS OR SYSTEMS, WHERE FAILURE OR MALFUNCTION MAY RESULT IN PERSONAL INJURY, DEATH, OR SEVERE PROPERTY OR ENVIRONMENTAL DAMAGE.**

Resale of ST products with provisions different from the statements and/or technical features set forth in this document shall immediately void any warranty granted by ST for the ST product or service described herein and shall not create or extend in any manner whatsoever, any liability of ST.

ST and the ST logo are trademarks or registered trademarks of ST in various countries.

Information in this document supersedes and replaces all information previously supplied.

The ST logo is a registered trademark of STMicroelectronics. All other names are the property of their respective owners.

© 2007 STMicroelectronics - All rights reserved

STMicroelectronics group of companies

Australia - Belgium - Brazil - Canada - China - Czech Republic - Finland - France - Germany - Hong Kong - India - Israel - Italy - Japan - Malaysia - Malta - Morocco - Singapore - Spain - Sweden - Switzerland - United Kingdom - United States of America

[www.st.com](http://www.st.com)